

Bakelite® PF 51

PF-NF

Momentive Specialty Chemicals

Product Texts**Product description:**

Phenolic moulding compound, organically filled, reinforced with cotton fibres, increased notched impact strength, standardized moulding compound.

Application areas:

Contact support power switch, switch covers magnetic switches, pulleys, tension/deflection pulleys, covers, handwheels.

Property Name	Value	Unit	Standard No.
Apparent density (moulding compound)	0.6	g/cm ³	ISO 60
Moulding shrinkage (compression moulding, longitudinal)	0.4	%	ISO 2577
Post shrinkage (compression moulding, 168h/110°C)	0.55	%	ISO 2577
Compr. strength (test spec. flat tested)	225	MPa	ISO 604
Flexural strength (2mm/min)	90	MPa	ISO 178
Flexural modulus	7500	MPa	ISO 178
Ball indentation hardness (H 961/30)	280	MPa	ISO 2039/P1
Water absorption (24h/23°C)	85	mg	similar to ISO 62

Additional characteristics:

Z, Typ, P

Preparation of Test Specimens of Thermosetting Moulding Compound

- Compression to ISO 295
- Injection to ISO 10724

Storage capability

2 years (relative humidity of 50-60% and maximum storage temperature of approximately 20°C)

Mechanical properties	Value	Unit	Test Standard
ISO Data			
Charpy impact strength (+23°C)	7	kJ/m ²	ISO 179/1eU
Charpy notched impact strength (+23°C)	2.7	kJ/m ²	ISO 179/1eA
Thermal properties			
ISO Data			
Temp. of deflection under load, 8.00 MPa	120	°C	ISO 75-1/-2
Electrical properties			
ISO Data			
Relative permittivity, 100Hz	16.5	-	IEC 60250
Dissipation factor, 100Hz	0.25	E-4	IEC 60250
Volume resistivity	1E9	Ohm*m	IEC 60093
Surface resistivity	1E10	Ohm	IEC 60093
Electric strength	9.5	kV/mm	IEC 60243-1
Comparative tracking index	125	-	IEC 60112
Other properties			
ISO Data			
Density	1420	kg/m ³	ISO 1183
Test specimen production			
ISO Data			

Bakelite® PF 51


PF-NF

Momentive Specialty Chemicals

Injection Molding, injection temperature	115	°C	ISO 10724
Injection Molding, injection velocity	170	mm/s	ISO 10724
Injection Molding, hold pressure	100	MPa	ISO 10724
Injection Molding, cure time	25	min	ISO 10724
Compression Molding, mold temperature	160	°C	ISO 295
Compression Molding, cure time	1	min	ISO 295

Diagrams

Dynamic Shear modulus-temperature

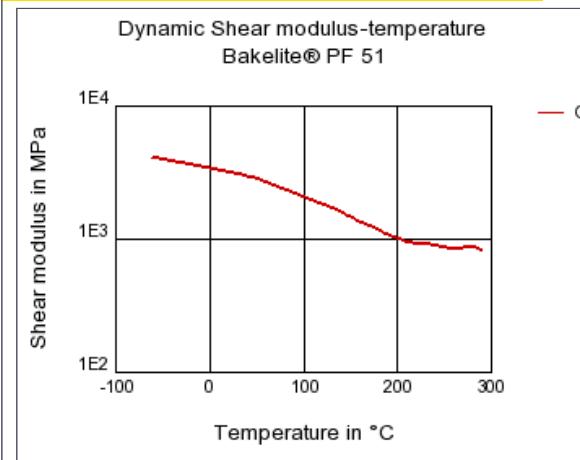

Characteristics

Processing

Injection Molding, Transfer Molding

Other text information

Injection Molding

VERARBEITUNG Temperature of material:	105-115	°C
Mould temperature:	160-190	°C
Curing time:	10-20	sec
 Further Information:		
Barrel temperature		
- Feed zone:	60-75	°C
- Nozzle zone:	80-100	°C
Cavity moulding pressure: d>	>15	MPa
Back pressure:	0.5-2	MPa
Holding pressure:	60% of injection pressure	

Compression molding

PROCESSING Mould temperature:	160-190	°C
Curing time:	20-40	sec
Cavity moulding pressure:	>15	MPa